

STUDIES ON STRUCTURAL BEHAVIOUR OF FLY ASH ADMIXED SFRC

Araja. Hampi
M.Tech Student,
Department of Civil Engineering,
Usha Rama College of Engineering & Technology, Telaprolu, Krishna District,
Andhra Pradesh, India, 521109

ABSTRACT: *The ever rising functional requirements of the structures and the capacity to resist aggressive elements has necessitated developing new cementations materials and concrete composites to meet the higher performance and durability criteria. The environmental factors and pressure of utilizing waste materials from industry have also been the major contributory factors in new developments in the field of concrete technology. In this direction, an attempt has been made in the present investigation to evaluate the workability, compressive strength, split tensile strength and flexure strength on addition of Fly Ash (0 – 30%) along with crimped steel fibers (0-1%) in concrete. Standard cubes of 150 X 150 X 150 mm have been cast and tested for obtaining 28 days and 60 days compressive strength. Standard cylinders of 150mm diameter and 300 mm height were cast and tested for Split tensile strength. Standard Beams of 500mmx100mmx100mm were cast and tested for Flexural strength. Results were analyzed to derive useful conclusions regarding the strength characteristics of Fly Ash fiber reinforced concrete.*

Key Words: *Fibre Reinforced Concrete, Fly Ash, Admixture, Concrete, Strength, Durability*

I. INTRODUCTION

The production of superior quality of Ordinary Portland Cement (OPC) in the country was primarily responsible for introducing the grading system in OPC by Bureau of Indian Standard (BIS) during 1986-87. The other varieties of structural cements, such as sulphate resisting Portland cement, Pozzolana cement and blast furnace slag cement found their way in the improvement of quality of prompted the structural engineers and major consumers to adopt higher grades of concretes in the construction work. This has been marked difference in the quality of concrete during this period primarily due to the availability of superior quality of cements in the market. The trend is continuing more and more varieties of cements are coming to the markets which help to the consumers to make appropriated grade quality of concrete to meet the specific construction requirement.

In the past continuous efforts were made to produce different kinds of cement, suitable for different situations by changing oxide composition and fineness of grinding. With the extensive use of cement, for widely varying conditions,

the types of cement that could be made only by varying the relative proportions of the oxide compositions were not found to be sufficient. Recourses have been taken to add one or two more new materials, known as additives, to the clinker at the time of grinding, or to the use of entirely different basic raw materials in the manufacture of cement. The use of additives, changing chemical composition, and use of different raw materials have resulted in the availability of many types of cements to cater to the need of the construction industries for specific purposes.

The most important Pozzolana materials are fly ash, silica fume and Metakaolin whose use in cement and concrete is thus likely to be a significant achievement in the development of concrete technology in the coming few decades. The high Performance fiber reinforced, polymer concrete composites and ready mixed concrete have been progressively introduced for specific applications. Though a lot of research is focused in the last decade on use of various admixtures in producing concrete, very little information is available on Fly Ash fiber reinforced concrete. As already mentioned, fly ash is an admixture: a pozzolana as it is generated as a by-product of combustion in coal power plants. Thus this waste material has lot of potential for use in concrete. Hence, there is need to study the strength and workability characteristics of FLY ASH-FRC (Fly Ash based fiber reinforced concrete). In this work experiments were planned to estimate the workability characteristics and various strength characteristics like compressive strength, Split tensile strength, and flexural strength.

II. METHODOLOGY

The scope of present investigation is to study and evaluate the effect of addition of Fly Ash (0, 10, 20 & 30%) and Crimped Steel Fibers (0, 0.5, 0.75 & 1%) in concrete. Cubes of standard size 150mmx150mmx150mm were cast and tested for 28 and 60 days compressive strength. Standard cylinders of size 150mm x 300mm were cast and tested for 28days and 60days split tensile strength. Also standard beams of size 500mm x100mm x 100mm were cast and were tested for 28 days and 60 days flexural strength

Materials Used:

Cement: - OPC Cement of 53-grade was used.

Coarse Aggregate: - Crushed granite metal with 50% passing 20mm and retained on 12.5mm sieve and 50%

passing 12.5mm and retained on 10mm sieve was used. Specific gravity of coarse aggregate was 2.75.

Fine aggregate: - River sand from local sources was used as fine aggregate. The specific gravity of sand is 2.68.

Water: - Potable fresh water, which is free from concentration of acid and organic substances was used for mixing the concrete.

Fiber: Steel Fibers is supplied by “STEWOLS INDIA (P) LTD, An ISO 9001: 2008 Company” at Nagpur. The most important parameter describing a fiber is its Aspect ratio. "Aspect ratio" is the length of fiber divided by an equivalent diameter of the fiber, where equivalent diameter is the diameter of the circle with an area equal to the cross sectional area of fiber. The properties of fiber reinforced concrete are very much affected by the type of fiber. Different types of fibers which have been tried to reinforce concrete are steel, carbon, asbestos, vegetable matter, polypropylene and glass. In the present investigation crimped round fibers used, Aspect ratio of 50.

Fly Ash: - Fly Ash is generated as a by-product of combustion in coal-fired power plants. It is obtained from the near -by thermal power plant.

Test Programme:

To evaluate the strength characteristics in terms of compressive, split tensile and flexural strengths, a total of 16 mixes were tried with different percentages of Fly Ash (0,10,20 & 30%) and different percentages of crimped steel fibers (0,0.5,0.75 & 1%). In all mixes the same type of aggregate i.e. crushed granite aggregate; river sand and the same proportion of fine aggregate to total aggregate are used. The relative proportions of cement, coarse aggregate, sand and water are obtained by IS - Code method. M30 is considered as the reference mix.

CASTING OF CUBES:

For each trail mix 3 cube specimens were cast for calculating 28 days strengths. The dimensions of specimen for cube are of 150mm x 150mm x 150mm.

CASTING OF CYLINDERS:

For each trail mix 3 cylinder specimens were cast for calculating 28 days strengths. The dimensions of the cylindrical specimen are of

Height = 300mm

Diameter = 150mm

CASTING OF BEAMS:

For each trail mix 3 beam specimens were cast for calculating 28 days strengths. The dimensions of the beam specimen are of 500mm x 100mm x 100mm.

III. RESULTS AND DISCUSSION

The results obtained from the experimental procedures were tabulated and presented below. The variations of parameters with respect to the percentage of admixtures are also shown in graphs below.

Compressive Strength: From the results it can be observed that the 28 days compressive strength increases

with the increase in the percentage of Fly Ash up to 20% addition level. On 20% addition of Fly Ash there is increase of cube compressive strength by 11.3% over plain concrete. At 10% level, the compressive strength has increased by 8.18%. But at 30% level, the compressive strength has decreased by 16.1%.

Effect of fibres on Compressive Strength: From the results it can be observed that with the increase in the percentage of fiber up to 0.75%, the compressive strength has increased by 10.2% over plain concrete. At 0.5% fiber volume the compressive strength has increased by 5.4% and at 1.00% fiber volume the compressive strength has increased by 9.7% respectively. Hence 0.75% of fiber volume can be taken as optimum content.

Split Tensile Strength: From the results it can be observed that the 28 days split tensile strength increases with the increase in the percentage of Fly Ash up to 20% addition level. On 20% addition of Fly Ash there is increase in split tensile strength by 8.92% over plain concrete. At 10% level, the split tensile strength has increased by 3.20%. But at 30% level, the split tensile strength has decreased by 15.8%.

Effect of fibres on Split Tensile Strength: From the results it can be observed that with the increase in the percentage of fiber up to 0.75%, the split tensile strength has increased by 29.75% over plain concrete. At 0.5% fiber volume the split tensile strength has increased by 21.51% and at 1.00% fiber volume the split tensile strength has increased by 24.94% respectively. Hence 0.75% of fiber volume can be taken as optimum content.

Flexural Strength: From the results it can be observed that the 28 days flexural strength increases with the increase in the percentage of Fly Ash up to 20% addition level. On 20% addition of Fly Ash there is increase of flexural strength by 8.93% over plain concrete. At 10% level, the flexural strength has increased by 5.83%. But at 30% level, the split tensile strength has decreased by 16.11

Effect of fibres on Flexural Strength: From the results it can be observed that with the increase in the percentage of fiber up to 0.75%, the flexural strength has increased by 30.48% over plain concrete. At 0.5% fiber volume the flexural strength has increased by 21% and at 1.00% fiber volume the flexural strength has 25.82% respectively. Hence 0.75% of fiber volume can be taken as optimum content.

Table 1 : 28 days Compressive Strength values in N/mm²

S.No	% of fibre	Compressive Strength (Mpa)			
		0% FLY ASH	10% FLY ASH	20% FLY ASH	30% FLY ASH
1	0.00% CSF	39.2	42.2	43.6	32.9
2	0.50% CSF	41.3	43.8	45.7	34.7

3	0.75% CSF	43.2	45.6	47.8	35.8
4	1.00% CSF	42.8	44.9	47.2	35.2

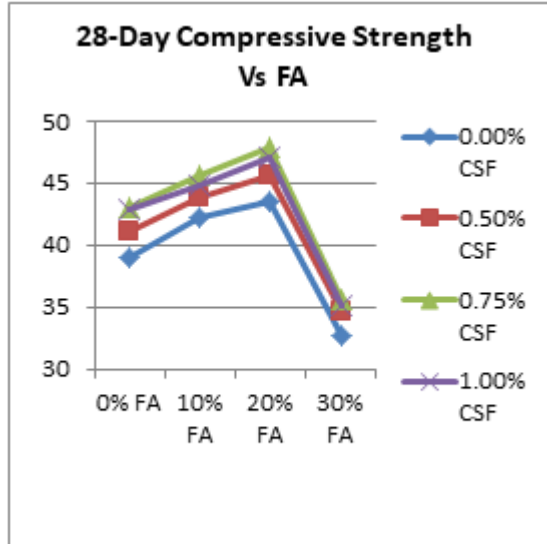


Figure 1: 28 Days Compressive Strength Vs % of FLY ASH

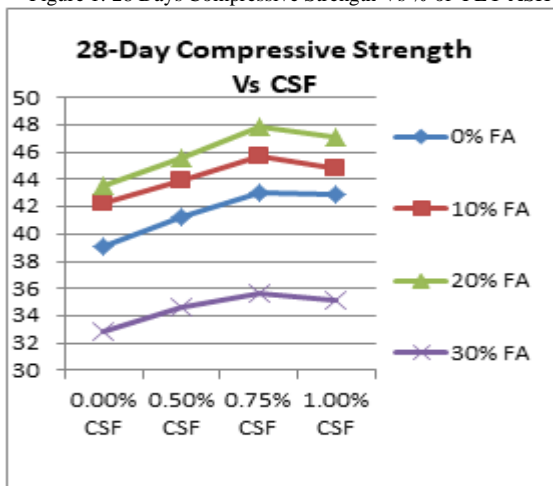


Figure 2: 28 Days Compressive Strength Vs % of CSF
 Table 2 : 28 days Split Tensile Strength values in N/mm²

S.No	% of fibre	Split Tensile Strength (Mpa)			
		0% FLY ASH	10% FLY ASH	20% FLY ASH	30% FLY ASH
1	0.00% CSF	4.35	4.52	4.74	3.64
2	0.50% CSF	5.32	5.58	5.81	4.44
3	0.75% CSF	5.64	5.82	6.22	4.67
4	1.00% CSF	5.26	5.65	6.05	4.66

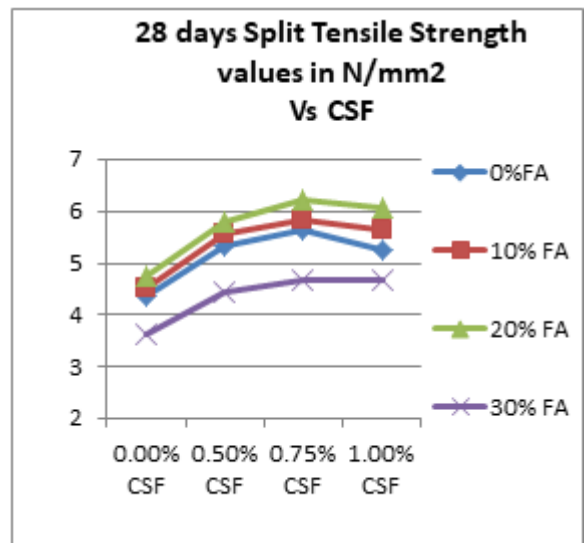


Figure 3: 28 Days Split Tensile Strength Vs % of CSF

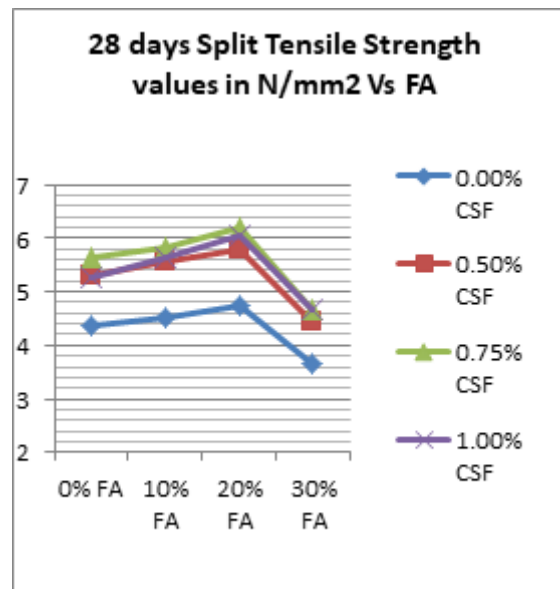


Figure 4: 28 Days Split Tensile Strength Vs % of FLY ASH

Table 3: 28 days Flexural Strength values in N/mm²

S.No	% of fibre	Flexural Strength (Mpa)			
		0% FLY ASH	10% FLY ASH	20% FLY ASH	30% FLY ASH
1	0.00% CSF	5.15	5.45	5.61	4.32
2	0.50% CSF	6.23	6.51	6.79	5.17
3	0.75% CSF	6.72	6.99	7.28	5.68
4	1.00% CSF	6.48	6.78	7.09	5.47

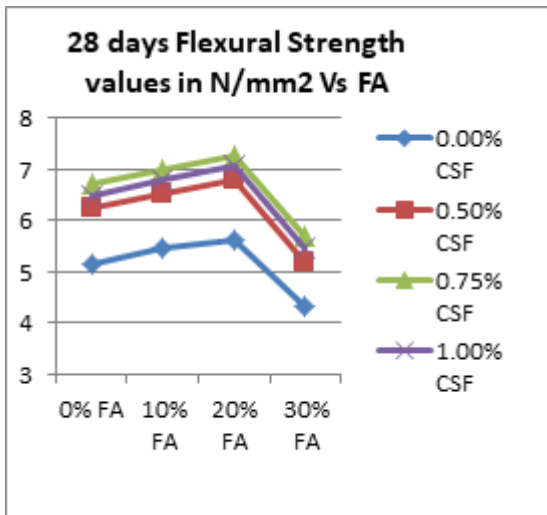


Figure 5: 28 Days Flexural Strength Vs % of FA

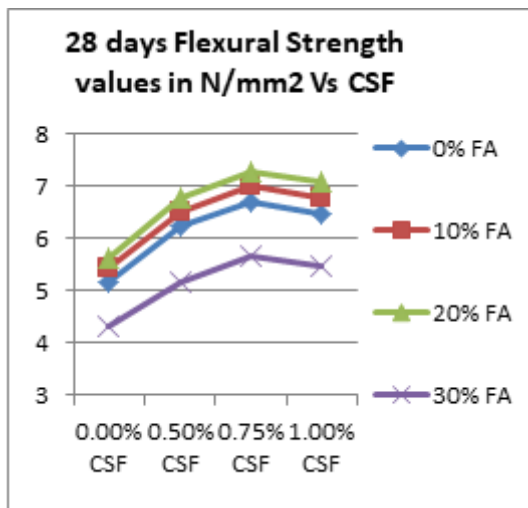


Figure 6: 28 Days Flexural Strength Vs % of CSF

IV. CONCLUSIONS

The workability of concrete measured from compaction factor degree. As the percentage of Fly Ash and steel fibre increases the compaction factor decreases. Hence it can be concluded that with the increase in the Fly Ash content and fiber content workability decreases. From the experimental results, the optimum percentage recommended is 0.75% steel fiber volume with 20% addition of in Fly Ash achieving maximum benefits in compressive strengths, split tensile strengths and flexural strengths.

The compressive strength of FLY ASH FRC mixes at 28 days shows maximum values with the addition of Fly Ash up to 20% level and with the addition of steel fibres up to 0.75% level when compared to that of plain concrete.

The split tensile strength of FLY ASH-FRC mixes at 28 days shows maximum values with the addition of Fly Ash up to 20% level and with the addition of steel fibres up to 0.75% level when compared to that of plain concrete.

The flexural strength of FLY ASH-FRC mixes at 28 days shows maximum values with the addition of Fly Ash up to

20% level and with the addition of steel fibres up to 0.75% level when compared to that of plain concrete.

Beyond 20% Fly ash and 0.75% steel fibres the strengths were observed to decrease. Hence these percentages were considered as optimum.

REFERENCES

- [1] Naik TR, Kraus RN (2000), "Use of Wood Ash for Structural Concrete and Flowable," Solid Waste Management and Research Program, CLSM, Report No. CBU-2000-31, Pp.121.
- [2] Colin D. Johnston (2001), "Fiber Reinforced Cements and Concretes" Advances in Concrete Technology, Gordon and Breach Science publishes, Vol.3, Pp.105-108.
- [3] Naik, T R Kraus, R N (2003), "A New Source of Pozzolanic Material", American Concrete Institute, ISSN: 0162-4075, OCLC: 4163061, Vol.25, No.12, Pp.55-62.
- [4] AntonieE.Naaman (2003), "Engineered Steel Fibres with Optimal Properties of Reinforcement of Cement Composites", Journal of Advanced Concrete Technology, Vol.1, No.3, Pp.241-252.
- [5] Mohamed-Ali Hasan (2006), "Potential of Fly Ash as an Additive in Concrete", Journal of Materials in Civil Engineering, Vol.18, No.4, Pp.605-611.
- [6] Paki Turgut (2007), "Cement composites with limestone dust and different grades of wood sawdust", Building and Environment, Vol.42, No.11, Pp.3801-3807.
- [7] Avancha Sri Sowmya, K. Sundara Kumar, "Studies On Strength Characteristics of Concrete with Metakoalin as an Admixture", International Research Journal of Engineering and Technology, (IRJET), Volume: 02 Issue: 09, Dec-2015.
- [8] IS 516-1959: standard methods for testing strength of concrete.
- [9] K. Sundara Kumar, Goriparthi Venkata Ramana, "Studies On Production Of Greener Concrete Using Agro-Industrial Waste", International Journal For Technological Research In Engineering, (IJTRE), Volume 4, Issue 2, October-2016.
- [10] K. Sundara Kumar, Sirivella Bindu Bhargavi, "Exploring The Strength Characteristics Of Concrete With Rapidite As An Admixture, International Journal For Technological Research In Engineering, (IJTRE), Volume 4, Issue 2, October-2016.
- [11] K. Sundara Kumar, M. Rajasekhar, "Studies On Making Of Sustainable Concrete Using Selected Industrial Wastes", International Journal For Technological Research In Engineering, (IJTRE), Volume 3, Issue 12, August-2016.
- [12] Pilli Narendra Babu, K. Sundara Kumar, "Studies On Strength Characteristics Of Concrete With "Sodium Nitrate" As An Admixture", International Journal For Technological Research In Engineering, (IJTRE), Volume 4, Issue 3, November-2016