

STUDIES ON STRENGTH CHARACTERISTICS OF FRC WITH WOOD WASTE ASH

P VAMSI KRISHNA
M. Tech Student
Department of Civil Engineering
URCET, Telaprolu, Krishna District,
Andhra Pradesh, India

Abstract: - Concrete has unlimited opportunities for innovative applications, design and construction techniques. Its great versatility and relative economy in filling wide range of needs has made it very competitive building material. The ever rising functional requirements of the structures and the capacity to resist aggressive elements has necessitated developing new cementations materials and concrete composites to meet the higher performance and durability criteria. The environmental factors and pressure of utilizing waste materials from industry have also been the major contributory factors in new developments in the field of concrete technology. In this direction, an attempt has been made in the present investigation to evaluate the workability, compressive strength, split tensile strength and flexure strength on addition of wood waste ash (0 – 30%) along with crimped steel fibers (0-1%) in concrete. Standard cubes of 150 X 150 X 150 mm have been cast and tested for obtaining 28 days compressive strength. Standard cylinders of 150mm diameter and 300 mm height were cast and tested for Split tensile strength. Standard Beams of 500mmx100mmx100mm were cast and tested for Flexural strength. Results were analyzed to derive useful conclusions regarding the strength characteristics of wood waste ash fiber reinforced concrete.

Keywords: - Fibre Reinforced Concrete, Wood Waste Ash, Admixture, Concrete, Strength, Durability.

I. INTRODUCTION

With the advancement of technology and increased field of applications of concrete and mortars, the strength workability, durability and other characters of the ordinary concrete need modifications to make it more suitable by situations. Added to this is the necessity to combat the increasing cost and scarcity of cement. Under these circumstances the use of admixtures is found to be an important alternative solution. The production of superior quality of Ordinary Portland Cement (OPC) in the country was primarily responsible for introducing the grading system in OPC by Bureau of Indian Standard (BIS) during 1986-87. The other varieties of structural cements, such as sulphate resisting Portland cement, Pozzolana cement and blast furnace slag cement found their way in the improve quality of prompted the structural engineers and major consumers to adopt higher grades of concretes in the construction work. This has been marked difference in the

quality of concrete during this period primarily due to the availability of superior quality of cements in the market. The trend is continuing more and more varieties of cements are coming to the markets which help to the consumers to make appropriated grade quality of concrete to meet the specific construction requirement. The high performance fiber reinforced, polymer concrete composites and ready mixed concrete have been progressively introduced for specific applications.

In the past continuous efforts were made to produce different kinds of cement, suitable for different situations by changing oxide composition and fineness of grinding. With the extensive use of cement, for widely varying conditions, the types of cement that could be made only by varying the relative proportions of the oxide compositions were not found to be sufficient. Recourses have been taken to add one or two more new materials, known as additives, to the clinker at the time of grinding, or to the use of entirely different basic raw materials in the manufacture of cement. The use of additives, changing chemical composition, and use of different raw materials have resulted in the availability of many types of cements to cater to the need of the construction industries for specific purposes. The most important Pozzolana materials are fly ash, silica fume and Metakaolin whose use in cement and concrete is thus likely to be a significant achievement in the development of concrete technology in the coming few decades. The high Performance fiber reinforced, polymer concrete composites and ready mixed concrete have been progressively introduced for specific applications.

II. MATERIALS

The scope of present investigation is to study and evaluate the effect of addition of wood waste ash (0, 10, 20 & 30%) and Crimped Steel Fibers (0, 0.5, 0.75 & 1%) in concrete. Cubes of standard size 150mmx150mmx150mm were cast and tested for 28 compressive strength. Standard cylinders of size 150mm x 300mm were cast and tested for 28days split tensile strength. Also standard beams of size 500mm x100mm x 100mm were cast and were tested for 28 days flexural strength

Materials Used

Cement: - OPC Cement of 53-grade was used. Coarse Aggregate: - Crushed granite metal with 50% passing 20mm and retained on 12.5mm sieve and 50% passing 12.5mm and retained on 10mm sieve was used. Specific gravity of coarse

aggregate was 2.75. Fine aggregate: - River sand from local sources was used as fine aggregate. The specific gravity of sand is 2.68. Water: - Potable fresh water, which is free from concentration of acid and organic substances was used for mixing the concrete. Fiber: Steel Fibers is supplied by "STEWOLS INDIA (P) LTD, An ISO 9001: 2008 Company" at Nagpur. The most important parameter describing a fiber is its Aspect ratio. "Aspect ratio" is the length of fiber divided by an equivalent diameter of the fiber, where equivalent diameter is the diameter of the circle with an area equal to the cross sectional area of fiber. The properties of fiber reinforced concrete are very much affected by the type of fiber. Different types of fibers which have been tried to reinforce concrete are steel, carbon, asbestos, vegetable matter, polypropylene and glass. In the present investigation crimped round fibers used, Aspect ratio of 50. Wood waste ash: - Wood waste ash is generated as a by-product of combustion in wood-fired power plants, paper mills, and other wood burning factories. In the present research the wood waste ash used, is detained from 300 microns.

S.No	% of fibres	Flexural Strength (Mpa)			
		0% WWA	10% WWA	20% WWA	30% WWA
1	0.00% CSF	5.15	5.45	5.61	4.32
2	0.50% CSF	6.23	6.51	6.79	5.17
3	0.75% CSF	6.72	6.99	7.28	5.68
4	1.00% CSF	6.48	6.78	7.09	5.47

III. METHODOLOGY

To evaluate the strength characteristics in terms of compressive, split tensile and flexural strengths, a total of 16 mixes were tried with different percentages of wood waste ash (0,10,20 & 30%) and different percentages of crimped steel fibers (0,0.5,0.75 & 1%). In all mixes the same type of aggregate i.e. crushed granite aggregate; river sand and the same proportion of fine aggregate to total aggregate are used. The relative proportions of cement, coarse aggregate, sand and water are obtained by IS - Code method. M30 is considered as the reference mix.

IV. RESULTS & DISCUSSION

The results obtained from the experimental procedures were tabulated and presented below. The variations of parameters with respect to the percentage of admixtures are also shown in graphs below

Table 1. 28 days Compressive Strength values in N/mm²

S.No	% of fibres	Compressive Strength (Mpa)			
		0% WWA	10% WWA	20% WWA	30% WWA
1	0.00% CSF	39.2	42.2	43.6	32.9
2	0.50% CSF	41.3	43.8	45.7	34.7
3	0.75% CSF	43.2	45.6	47.8	35.8
4	1.00% CSF	42.8	44.9	47.2	35.2

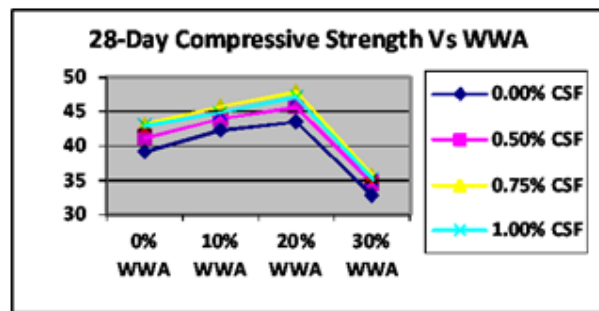


Fig.1 Compressive strength Vs WWA

Table 2. 28 days Split Tensile Strength values in N/mm²

S.No	% of fibres	Split Tensile Strength (Mpa)			
		0% WWA	10% WWA	20% WWA	30% WWA
1	0.00% CSF	4.35	4.52	4.74	3.64
2	0.50% CSF	5.32	5.58	5.81	4.44
3	0.75% CSF	5.64	5.82	6.22	4.67
4	1.00% CSF	5.26	5.65	6.05	4.66

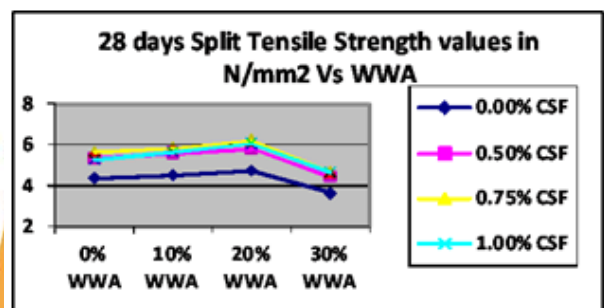


Fig.2 Split Tensile Strength Vs WWA

Table 3. 28 days Flexural Strength values in N/mm²

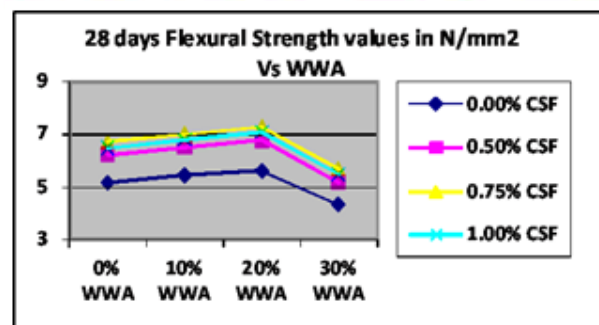


Fig.3 Flexural Strength Vs WWA

Effect of addition of wood Waste ash on Compressive Strength: From Figure 1 it can be observed that the 28 days compressive strength increases with the increase in the percentage of wood waste ash up to 20% addition level. On 20% addition of wood waste ash there is increase of cube compressive strength by 11.3% over plain concrete. At 10% level, the compressive strength has increased by 8.18%. But at 30% level, the compressive strength has decreased by 16.1%. Effect of addition of wood waste ash on Split Tensile Strength: From Figure 2 it can be observed that the 28 days split tensile strength increases with the increase in the percentage of wood waste ash up to 20% addition level. On

20% addition of wood waste ash there is increase in split tensile strength by 8.92% over plain concrete. At 10% level, the split tensile strength has increased by 3.20%. But at 30% level, the split tensile strength has decreased by 15.8%.

Effect of addition of wood waste ash on Flexural Strength: From Figure 3 it can be observed that the 28 days flexural strength increases with the increase in the percentage of wood waste ash up to 20% addition level. On 20% addition of wood waste ash there is increase of flexural strength by 8.93% over plain concrete. At 10% level, the flexural strength has increased by 5.83%. But at 30% level, the split tensile strength has decreased by 16.11%.

V. CONCLUSIONS

Results were analyzed to derive useful conclusions regarding the strength characteristics of wood waste ash fiber reinforced concrete (WWA-FRC). M30 concrete has been used as reference mix. The following conclusions may be drawn from the study on strength characteristics of wood waste ash fibre reinforced concrete properties.

The compressive strength of WWAFRC mixes at 28 days increased with the addition of wood waste ash up to 20% level when compared to that of plain concrete. Hence for normal concreting works we can go up to 20% addition level of wood waste ash. The maximum percentage increase over plain concrete is 22.50% and the percentage increase ranges from 11.25 to 22.50% over plain mix. Similar trends were observed even at 60 days age. The maximum percentage increase over plain concrete is 26.33% and the percentage increase ranges from 11.83 to 26.33% over plain mix.

The split tensile strength of WWA-FRC mixes at 28 days increased with the addition of wood waste ash up to 20% level when compared to that of plain concrete. The maximum percentage increase over plain concrete is 43.47% and the percentage increase ranges from 8.92 to 43.47% over nominal mix. Similar trends were observed even at 90 days age. The maximum percentage increase over plain concrete is 49% and the percentage increase ranges from 7.54 to 49% over nominal mix.

The flexural strength of WWA-FRC mixes at 28 days increased with the addition of wood waste ash up to 20% level when compared to that of plain concrete. The maximum percentage increase over plain concrete is 41.36% and the percentage increase ranges from 8.93 to 41.36% over normal mix. Similar trends were observed even at 60 days age. The maximum percentage increase over plain concrete is 46.45% and the percentage increase ranges from 7.83 to 46.45% over normal mix.

REFERENCES

- [1] Naik TR, Kraus RN (2000), "Use of Wood Ash for Structural Concrete and Flowable," Solid Waste Management and Research Program, CLSM, Report No. CBU-2000-31, Pp.121.
- [2] Colin D. Johnston (2001), "Fiber Reinforced Cements and Concretes" Advances in Concrete Technology, Gordon and Breach Science publishes, Vol.3, Pp.105-108.

- [3] Naik, T R Kraus, R N (2003), "A New Source of Pozzolanic Material", American Concrete Institute, ISSN: 0162- 4075, OCLC: 4163061, Vol.25, No.12, Pp.55-62.
- [4] AntonieE.Naaman (2003), "Engineered Steel Fibres with Optimal Properties of Reinforcement of Cement Composites", Journal of Advanced Concrete Technology, Vol.1, No.3, Pp.241-252.
- [5] Mohamed-Ali Hasan (2006), "Potential of Wood Waste Ash as an Additive in Concrete", Journal of Materials in Civil Engineering, Vol.18, No.4, Pp.605-611.
- [6] Paki Turgut (2007), "Cement composites with limestone dust and different grades of wood sawdust", Building and Environment, Vol.42, No.11, Pp.3801-3807.
- [7] Emmanuel A. Okunade (2008), "The Effect of Wood Ash and Sawdust Admixtures on the Engineering Properties of a Burnt Laterite-Clay Brick", Journal of Applied Sciences, No.8,Pp.1042-1048.
- [8] Chee Ban Cheah, Mahyuddin Ramli (2011), "The implementation of wood Waste ash as a partial cement replacement material in the production of structural grade concrete and mortar", Resources, Conservation and Recycling, Vol.55, No.7, Pp.669-685.
- [9] Ek.Serafimova, M.Mladenov, I.Mihailova, Y.Pelovski (2011), "Study on the Characteristics of Waste Wood Ash", Journal of the University of Chemical Technology and Metallurgy, Vol.41, No.1, Pp.31-34.
- [10] Udoeyo FF, Inyang H,Yung DT,Oparadu EE(2006), "Potential of Wood Waste Ash as an Additive on Infrastructural Development and Environment" University of Philippines, Building Materials, Vol.23, Pp 2641-2646.